

Maximum Service Temperature of KYDEX® Sheet

For information applicable to KYDEX® FST please refer to 300 series technical briefs.

TB - 121-A

Introduction

The heat deflection temperature (HDT) of a material is the temperature at which a formed or molded part or flat sheet will begin to lose its shape when subjected to temperature and load. HDT may serve as an estimate of the maximum service temperature of the material. ASTM D-648, Standard Test Method for Deflection Temperature of Plastics Under Flexural Load, is a HDT method used by SEKISUI SPI to estimate the maximum service temperature for various grades of KYDEX® sheet.

ASTM D648 is used to estimate how a given plastic will behave at an elevated temperature for a short period of time and to compare different polymers under identical conditions. With this method, a bar of rectangular cross section is tested as a simple beam with the load applied at its center to give maximum fiber stresses of 455 kPa (66 psi) or 1820 kPa (264 psi). The specimen is immersed under load in a heat-transfer medium provided with means of raising the temperature at 120°C (248°F)/hour. The HDT occurs when the test bar has deflected 0.25mm (0.010”).

Actual deflection temperatures will vary due to internal and external stresses, part design, and application. Thermoforming can increase or decrease a part's HDT. If the core of the material is not heated to the proper forming temperature or the part is cooled too quickly, more stresses will be present in the sheet and thus lower the overall HDT of the part.

Samples are typically tested as annealed and/or unannealed. By annealing the sample at 66°C (150°F) for 8 hours, the stresses in the sheet are relaxed and a maximum short-term service temperature is established. An unannealed value represents the minimum short-term service temperature. Depending upon how the parts are processed will determine where in the range of annealed and unannealed values that the part will fall.

*For actual maximum service temperatures, each part should be tested for suitability.

SEKISUI SPI

ISO 9001 and 14001 Certified

Customer Service

6685 Low St, Bloomsburg, PA 17815 USA

Phone: 800.325.3133, +1.570.389.5810

Outside the US: +1.570.389.5814

Fax: 800.452.0155, +1.570.387.7786

Email: info@sekisui-spi.com

Technical Service

Phone: 800.682.8758

Fax: +1.570.387.8722

Outside the US: +1.570.387.6997

techservice@sekisui-spi.com

sekisui-spi.com


Maximum Service Temperature of KYDEX® Sheet

For information applicable to KYDEX® FST please refer to 300 series technical briefs.

TB - 121-A

HDT Ranges for Various Grades of KYDEX® Sheet

Tested at 1820 kPa (264 psi)

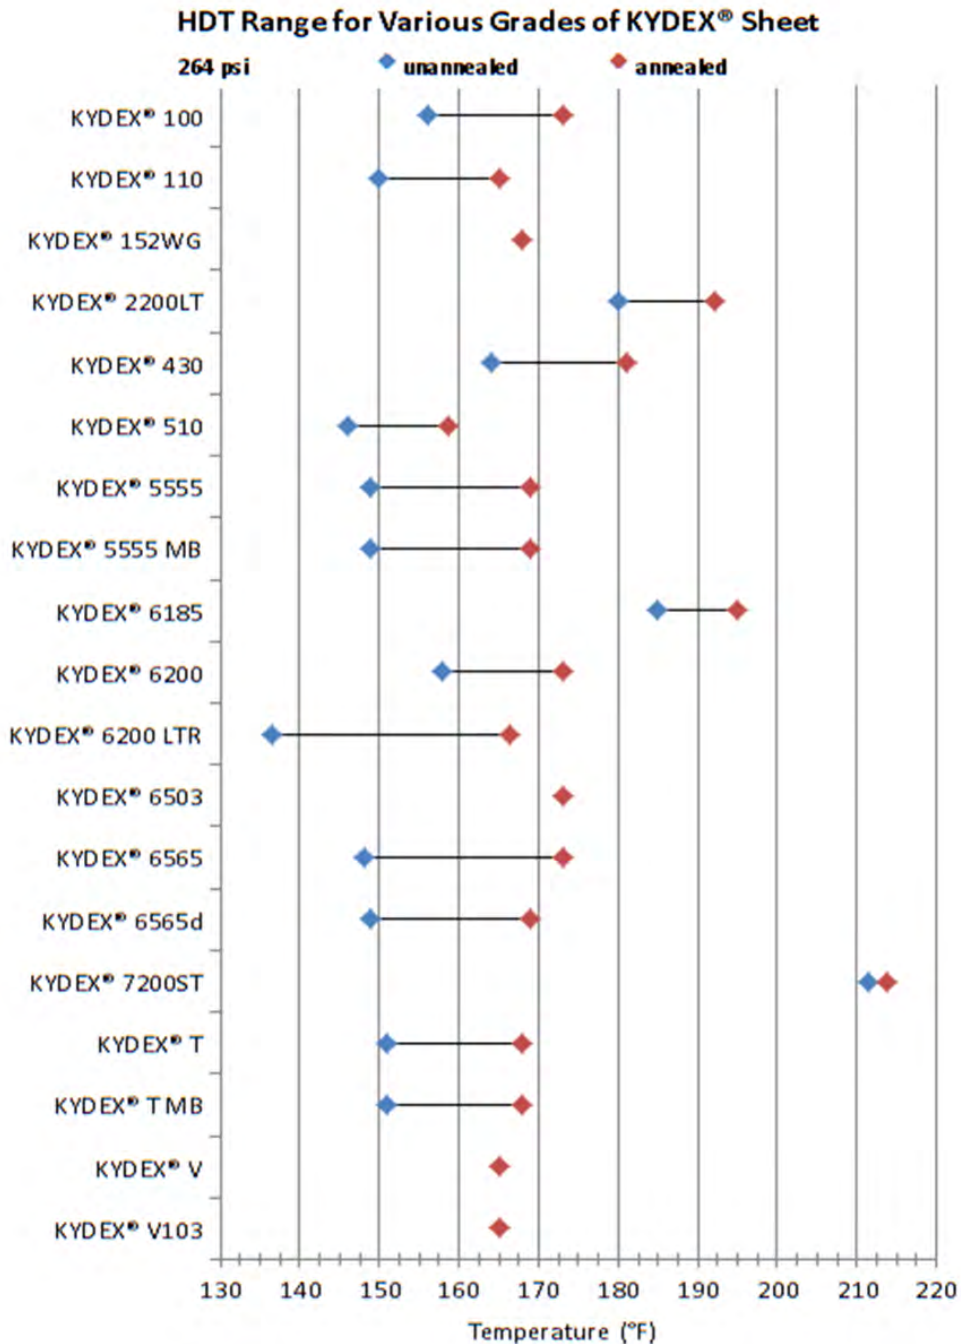

SEKISUI SPI
ISO 9001 and 14001 Certified

Customer Service
6685 Low St, Bloomsburg, PA 17815 USA
Phone: 800.325.3133, +1.570.389.5810
Outside the US: +1.570.389.5814
Fax: 800.452.0155, +1.570.387.7786
Email: info@sekisui-spi.com

Technical Service
Phone: 800.682.8758
Fax: +1.570.387.8722
Outside the US: +1.570.387.6997
techservice@sekisui-spi.com

sekisui-spi.com

Because we cannot anticipate or control the many different conditions under which this information and our products may be used, we do not guarantee the applicability of the accuracy of this information or the suitability of our products in any given situation. Users should conduct their own tests to determine the suitability of each product for their particular purposes. Data in the physical property table represents typical values and are to serve only as a guide for engineering design. Results are obtained from specimens under ideal laboratory conditions. Right to change physical properties as a result of technical progress is reserved. THE PRODUCTS DISCUSSED ARE SOLD WITHOUT WARRANTY OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR USE, EITHER EXPRESSED OR IMPLIED, EXCEPT AS PROVIDED IN OUR STANDARD TERMS AND CONDITIONS OF SALE. Buyer assumes all responsibility for loss or damage arising from the handling and use of our products, whether done in accordance with directions or not. In no event shall the supplier or the manufacturer be liable for incidental or consequential damages. Also, statements concerning the possible use of our products are not intended as recommendations to use our products in the infringement of any patent. Consult local code and regulatory agencies for specific requirements regarding code compliance, transporting, processing, recycling and disposal of our product. Product not intended for use as a heat resistant surface. Texture, product grade and other conditions may cause variations in appearance.

This information supersedes all previously published data.